

Communication

Fatigue Resistance of Dissected Lower First Molars Restored with Direct Fiber-Reinforced Bridges—An In Vitro Pilot Study

Veronika T. Szabó ^{1,†}, Balázs Szabó ^{2,†}, Noémi Barcsayné-Tátrai ¹, Csongor Mészáros ¹, Gábor Braunitzer ³, Balázs P. Szabó ⁴, Lippo Lassila ⁵, Sufyan Garoushi ^{5,‡} and Márk Fráter ^{1,*,‡}

¹ Department of Operative and Esthetic Dentistry, Faculty of Dentistry, University of Szeged, H-6720 Szeged, Hungary; tszaboveronika@gmail.com (V.T.S.); noncsi817@gmail.com (N.B.-T.); csongor021@gmail.com (C.M.)

² Department of Periodontology, Faculty of Dentistry, University of Szeged, H-6720 Szeged, Hungary; drszabobalazs77@gmail.com

³ DicomLAB Dental Ltd., H-6726 Szeged, Hungary; braunitzergabor@gmail.com

⁴ Department of Food Engineering, Faculty of Engineering, University of Szeged, H-6725 Szeged, Hungary; szpb@mk.u-szeged.hu

⁵ Department of Biomaterials Science and Turku Clinical Biomaterials Center—TCBC, Institute of Dentistry, University of Turku, FI-20520 Turku, Finland; liplas@utu.fi (L.L.); sufgar@utu.fi (S.G.)

* Correspondence: meddentist.fm@gmail.com

† These authors contributed equally to this work.

‡ These authors also contributed equally to this work.

Abstract: The aim of this research was to evaluate the mechanical impact of utilizing different fiber-reinforced composite (FRC) systems to reinforce inlay-retained bridges in dissected lower molars with different levels of periodontal support. A total of 24 lower first molars and 24 lower second premolars were included in this study. The distal canal of all molars received endodontic treatment. After root canal treatment, the teeth were dissected, and only the distal halves were kept. Standardized class II occluso-distal (OD) (premolars) and mesio-occlusal (MO) (dissected molars) cavities were prepared in all teeth, and premolar–molar units were created. The units were randomly distributed among four groups ($n = \text{six}/\text{group}$). With the aid of a transparent silicone index, direct inlay-retained composite bridges were fabricated. In Groups 1 and 2, both discontinuous (everX Flow) and continuous (everStick C&B) fibers were used for reinforcement, while in Groups 3 and 4, only discontinuous fibers (everX Flow) were used. The restored units were embedded in methacrylate resin, simulating either physiological periodontal conditions or furcation involvement. Subsequently, all units underwent fatigue survival testing in a cyclic loading machine until fracture, or a total of 40,000 cycles. Kaplan–Meyer survival analyses were conducted, followed by pairwise log-rank post hoc comparisons. Fracture patterns were evaluated visually and with scanning electron microscopy. In terms of survival, Group 2 performed significantly better than Groups 3 and 4 ($p < 0.05$), while there was no significant difference between the other groups. In the case of impaired periodontal support, a combination of both continuous and discontinuous short FRC systems increased the fatigue resistance of direct inlay-retained composite bridges compared to bridges that only contained short fibers. Such a difference was not found in the case of sound periodontal support between the two different bridges.

Keywords: molar dissection; short fiber-reinforced composite; inlay-retained bridge; fatigue resistance; periodontal support; furcation involvement



Citation: Szabó, V.T.; Szabó, B.; Barcsayné-Tátrai, N.; Mészáros, C.; Braunitzer, G.; Szabó, B.P.; Lassila, L.; Garoushi, S.; Fráter, M. Fatigue Resistance of Dissected Lower First Molars Restored with Direct Fiber-Reinforced Bridges—An In Vitro Pilot Study. *Polymers* **2023**, *15*, 1343. <https://doi.org/10.3390/polym15061343>

Academic Editor: Haw-Ming Huang

Received: 22 January 2023

Revised: 2 March 2023

Accepted: 3 March 2023

Published: 8 March 2023



Copyright: © 2023 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

In the past few decades, the popularity and availability of implant-retained restorations has escalated. However, the number of complications (peri-implantitis and peri-implant mucositis) associated with their use has also increased [1,2]. It is also known that the

success rates of implants in periodontal patients lag behind the success rates seen in periodontally unaffected patients [3]. Due to the above mentioned reasons, patients still prefer to keep their own dentition. Thanks to modern approaches and armamentarium of restorative dentistry, it is now possible to conservatively treat many situations that would once have inevitably led to extraction [4]. Resective surgical approaches, such as dissection, are still worth considering as clinically relevant treatment options versus extraction and implant placement [5,6]. The dissection of a lower molar tooth, for either endodontic or periodontal reasons, aiming to preserve part of it after the removal of the non-savable part is an intervention that serves such a purpose. According to DeSanctis and colleagues, endodontic indications include endodontic failure (perforation, file separation, etc.), root caries, resorption, and fracture [7]. In such cases, the alveolar bone around the remaining root is usually predominantly intact. According to the findings of Carnevale and colleagues, periodontal indications can be severe furcation involvement, severe bone loss simultaneously affecting one or more roots, and severe recession or fenestration [8]. In these cases, the amount of alveolar bone around the retained root significantly affects the material choice and the type of restoration [9]. Some root resection studies with 5–10 years of follow-up showed success rates of 62–100%, which is quite promising in such a demanding situation [10]. When dissection is performed on a lower molar tooth, in most cases, the restoration is extended toward the direction of the removed root, possibly involving the neighboring one also. Since on many occasions the neighboring tooth is intact (or contains only a minor conservative restoration), restoring the edentulous span with an intracoronally retained bridge could be an ideal solution for such situations, following the principle of minimally invasive dentistry. Minimally invasive FRC bridges appear to be a good choice for restoring the affected edentulous span, as they are considered viable medium-term management alternatives for replacing single anterior or posterior teeth to traditional porcelain-fused-to-metal bridges [11]. An obvious and also widely used approach is to prepare an indirect restoration after digital or conventional impression taking. However, there is an increasing amount of evidence to support the use of fiber-reinforced direct restorations for more extensive defects [12]. Such restorations offer the advantages of minimally invasive preparations, lower costs, faster workflows, and better repairability. Furthermore, the mechanical, aesthetic, and handling properties of dental composites have shown a rapid development over the past few decades [13]. Since the development of pre-impregnated fiber bundles more than 20 years ago, the reinforcement of composites has gained increasing interest [14,15]. So far, limited information is available on their longevity and clinical behavior, but the available clinical studies of fiber-reinforced composite (FRC) fixed partial dentures demonstrate a high overall survival with predictable performance outcomes when used as a medium-term management alternative for replacing single anterior or posterior teeth [11]. The five-year survival rates of FRC bridges range between 73 and 93% [16,17].

Traditionally, continuous fibers are used for the reinforcement of direct inlay-retained composite bridges. Studies so far have focused on the type of long fibers incorporated in the bridge [18,19], the different framework designs with different fiber orientation [20,21], and the effect of the material and the occlusal morphology of the pontic [22]. The purpose of unidirectional long fibers is to improve the mechanical properties of the direct composite bridges. Whenever the clinical situation enables the usage of unidirectional long fibers, they are the best to achieve reinforcement within the structure of the restoration. This is due to the fact that unidirectional fibers give anisotropic mechanical properties to the composite and are known to be suitable for applications where the highest stress occurs. Reinforcing efficiency, evaluated by the Krenchel's factor, of unidirectional fibers is theoretically 100%, which means that reinforcing properties can be achieved and concentrated in one distinctive direction.

However, discontinuous, short fiber-reinforced composites (SFRCs) have been utilized for various other restorative purposes lately [23–26]. SFRC materials hold the promise of crack-arresting within the SFRC structure due to specific, unique features of the material,

such as aspect ratio, critical fiber length, fiber loading, fiber orientation, and adhesion between the matrix and the fiber [27,28]. This is actually measurable in the remarkable fracture toughness values of these materials. Fracture toughness is a property of the material that describes the resistance of brittle materials to the catastrophic propagation of flaws under loading, which therefore shows the damage tolerance of the material [27]. This means that a material with a high fracture toughness is able to resist crack initiation and propagation. Since the fibers are orientated randomly in SFRCs, the mechanical properties as well as the ability for potential reinforcement are equal in all directions and are three-dimensionally isotropic [29]. The features/characteristics of these two distinctive fibers are listed in Table 1. According to the manufacturer's instructions, fibers should be covered with particulate-filled composites (PFCs) from all directions to avoid moisture uptake from the oral cavity. Yet, more and more studies show that the fracture and fatigue resistance of a restoration can be improved when the flowable SFRC is not covered with PFC [30–33]. Thus, the question arises whether SFRCs could be utilized to improve an FRC bridge. To the best of our knowledge, no one has yet tested the flowable SFRC in combination with long fibers to fabricate a direct inlay-retained bridge for restorative purposes. Furthermore, different bone levels have not been simulated in such a restorative situation at all. These give novelty to the proposed study design.

Table 1. The investigated fiber-reinforced materials.

Material	Manufacturer	Fiber Orientation	Composition/Fibers Feature *	Mechanical Characteristics *
EverStick C&B	Stick Tech Ltd., GC Group member, Turku, Finland	Unidirectional	Pre-impregnated bundle (1.5 mm) of silanized E-glass fibers (65 vol%) with Bis-GMA, PMMA. \approx 4000 individual glass fibres (\varnothing 15 μ m) per bundle.	FS: 700–800 MPa FM: 15 GPa FT: not available
EverX Flow	GC, Tokyo, Japan	Multi-directional	Bis-EMA, TEGDMA, UDMA, short glass fiber (25 wt%, length 200–300 μ m and \varnothing 7 μ m), and barium glass.	FS: 146 MPa FM: 9 GPa FT: 2.8 MPa/mm ^{0.5}

Bis-GMA, bisphenol-A-glycidyl dimethacrylate; PMMA, polymethylmethacrylate; TEGDMA, triethylene glycol dimethacrylate; UDMA, urethane dimethacrylate; Bis-EMA, ethoxylated bisphenol-A-dimethacrylate; wt%, weight percentage; and vol%, volume percentage. FS, flexural strength; FM, flexural modulus; and FT, fracture toughness. * according to manufacturer data.

We aimed to investigate whether continuous or short and discontinuous fibers are better to reinforce inlay-retained direct bridges in terms of fatigue resistance and fracture patterns. We also sought to investigate how periodontal support may influence this.

The null hypotheses were that there would be no difference between the test groups either in (1) fatigue resistance or (2) in the fracture patterns.

2. Materials and Methods

2.1. Sample Selection

All procedures of the study were approved by the Ethics Committee of the University of Szeged (approval no. 4029), and the study was designed in accordance with the Declaration of Helsinki.

In our study, 24 mandibular second premolars and 24 mandibular first molars, previously extracted due to periodontal or orthodontic reasons, were selected and included. All teeth were used within 6 months of extraction. Soft tissue residues, cementum, and calculus covering the root surfaces were removed with hand and ultrasonic scalers. Until they were used, the teeth were stored in 0.9% saline solution at room temperature.

The primary inclusion criteria were the visual absence of caries or root cracks, previous endodontic treatment, posts or crown, or resorptions. Regarding the coronal dimensions of the molar teeth, approximately 90% of the specimens ranged from 10 to 10.9 mm in the bucco-lingual dimension, and the rest were between 11 and 12 mm. The mesio-distal dimension of the specimens was also measured; a mean was calculated and specimens that fell within the \pm 10% range of the mean were included. The height of the specimens was

between 8 and 9 mm measured from the cemento-enamel junction (CEJ). The length of the distal roots fell in the 14–16 mm range. Regarding the coronal dimensions of the premolars, 90% of the teeth ranged between 9 and 10 mm in the bucco-lingual dimension. As for the mesio-distal dimension, 90% of the samples measured between 7 and 7.5 mm [24,30].

2.2. Sample Preparation

All procedures were performed by the same trained operator. The lower first molars were dissected with a vertical cut through the oro-vestibular bisector of the crown toward the fornix, and only the distal tooth halves were kept for further procedures.

The sectioned surfaces were smoothed to have a cleansable non-retentive surface. In the hemisected distal tooth halves, the pulp chambers were deroofed and endodontic treatment of the distal canal(s) was performed according to our previous protocol [34]. The root canals were instrumented with Pathfiles (1-2-3) and ProTaper (S1-S2-F1-F2-F3) (Dentsply Maillefer, Ballaigues, Switzerland) to the working length. The specimens were irrigated with 5% NaOCl alternating with 10% EDTA (ethylenediaminetetraacetic acid) with a 2 mL syringe and 25-gauge needle. Root canal filling was performed by matched-single-cone obturation with a master cone matching the final instrument used for preparation and sealer (AH plus; Dentsply Maillefer).

In the hemisected distal tooth halves, standardized mesio-occlusal (MO) in all premolars occluso-distal (OD) cavities was prepared according to Cara et al. [35].

All specimens received the same adhesive treatment. The pulp chambers of the dissected molars and the proximal boxes of the premolars were roughened with a carbide bur, cleaned, and after selective enamel etching for 15 sec with 37% orthophosphoric acid, a one-step self-etch adhesive system was applied (G-Premio Bond, GC Europe, Leuven, Belgium) according to manufacturer's instructions. The adhesive was light-cured for 40 s using an Optilux 501 quartz-tungsten-halogen light-curing unit (Kerr Corp., Orange, CA, USA). The average power density of the light source, measured with a digital radiometer (Jetlite light tester; J. Morita USA Inc., Irvine, CA, USA) before the bonding procedure, was 840 ± 26.8 mW/cm². After photopolymerization, the proximal boxes and the pulp chambers were filled up to the level of the occluso-pulpal wall with a composite filling material (G-aenial Posterior A3, GC Europe) and light-cured for 20 s.

2.3. Direct Bridge Fabrication

The premolars and dissected molars were paired, forming units, and fixed in a gypsum block using light body silicone impression material. Silicone was an ideal solution for fixing, as the roots could be completely and easily removed from it at any time during the procedures, aiding handling of the samples (Figure 1A). In order to standardize the size and the shape of the direct, inlay-retained bridges, a transparent silicone index was individually made for each sample in the following way: a laboratory-technician-made prefabricated, inlay-retained composite bridge was placed into the cavities of each unit (Figure 1B), all potential gaps were blocked out with a temporary filling material, and a template was made from a transparent silicone impression material (Exaclear, GC Europe) to obtain a silicone index of the future restoration (Figure 1C). After setting, the silicone index was sectioned horizontally at the equator with a scalpel and the bridge was removed (Figure 1D).

During the fabrication of the inlay-retained bridges different FRC were applied (Table 1) with different designs (the utilized materials and designs are summarized in Table 2).

In Groups 1 and 2, after the adhesive treatment of the cavities (see above), a flowable SFRC material (everX Flow dentin shade, GC Europe) was molded to the horizontally cut silicone index to create the gingival part of the pontic to the level of the occlusal boxes of the teeth and was then photopolymerized for 40 s. Then, a flowable SFRC was applied to the walls of the prepared cavities covering the cervical and one third of the box. After this, a bundle of long, unidirectional FRC (everStick C&B, GC Europe) was cut at the appropriate length, placed in position, and photopolymerized. The remaining occlusal, two thirds of the bridge, was molded using a flowable SFRC again, and photopolymerization (40 s) of

the last occlusal layer was performed through the transparent silicone index to standardize the occlusal anatomy. The restorations were finished with fine granular diamond burs (FG 7406-018, Jet Diamonds, USA and FG 249-F012, Horico, Germany) and aluminum oxide polishers (OneGloss PS Midi, Shofu Dental GmbH, Ratingen, Germany) (Figure 2).

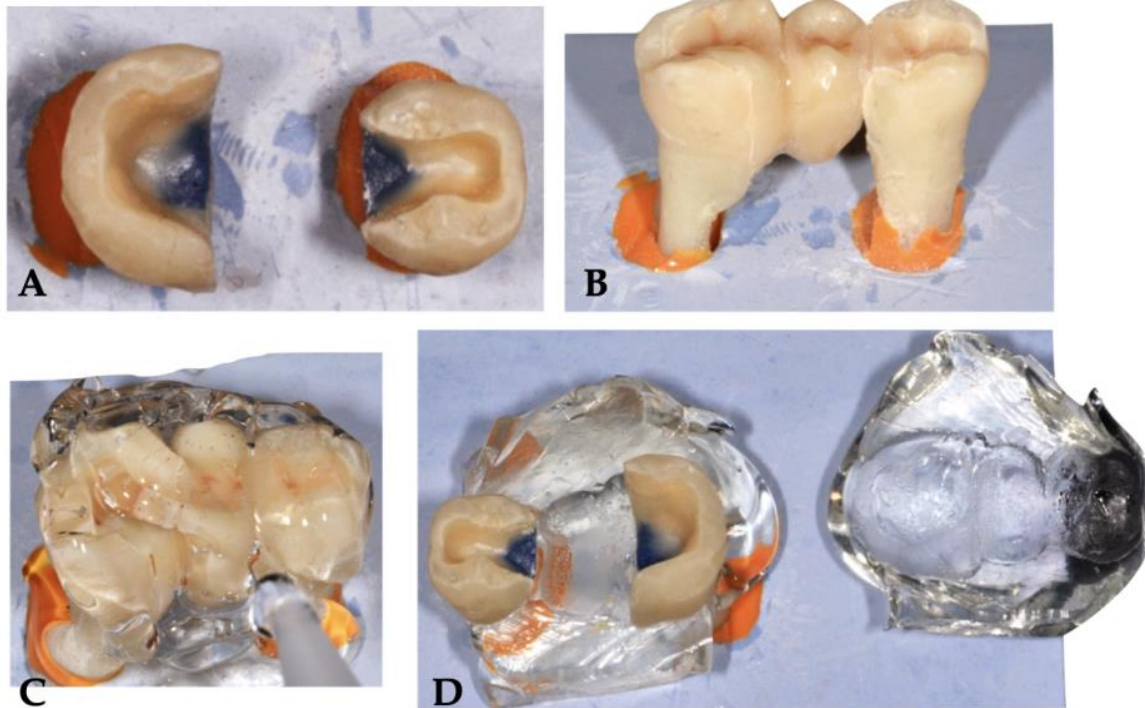


Figure 1. Steps of fabricating a standardized, transparent silicone index to help the fabrication of the future direct, inlay-retained bridges.

Table 2. In Groups 1 and 2, both continuous and discontinuous short glass fibers were used, while in Groups 3 and 4 only discontinuous short fibers were used during the restorative procedure.

	Group 1 and 2	Group 3 and 4
Pontic base	EverX flow dentin shade (discontinuous, short fibers)	EverX flow dentin shade (discontinuous, short fibers)
Central glass fibers	EverStick C&B (continuous fibers)	EverX flow dentin shade (discontinuous, short fibers)
Occlusal anatomy	EverX flow dentin shade (discontinuous, short fibers)	EverX flow dentin shade (discontinuous, short fibers)



Figure 2. The standardized direct FRC bridges were finished and polished.

In Groups 3 and 4, the direct composite bridges were made of only a flowable SFRC (everX Flow dentin shade). The clear silicone indexes were created in the aforementioned way, but instead of the horizontal cut, only 3 holes were punched in them through which the tip of the flowable SFRC was inserted, and the bridge was molded. After the adhesive treatment of the cavities (see above), the negative space encapsulated by the clear silicone index was molded incrementally by the flowable SFRC. Photopolymerization was made through the transparent silicone index. Each layer was light-cured for 40 s. The restorations were finished and polished the same way as in Group 1 and 2.

2.4. Embedding of the Samples

All units restored in the aforementioned way were embedded in a special methacrylate resin (Technovit 4004, Heraeus-Kulzer, Wertheim, Germany) in the following way: samples of Groups 1 and 3 were embedded in accordance with intact periodontal conditions 2 mm from the CEJ, while in Group 2 and 4, embedding was performed and the level of embedding was set at 6 mm apical to the CEJ, simulating furcation involvement [34,36]. The simulation of periodontal ligaments was achieved with a latex separating liquid (Rubber-Sep, Kerr, Orange, CA, USA), which was applied in one layer to the roots according to the level of the planned embedding, before embedding [34,37].

The 4 study groups with the corresponding levels of embedding are shown in Figure 3.

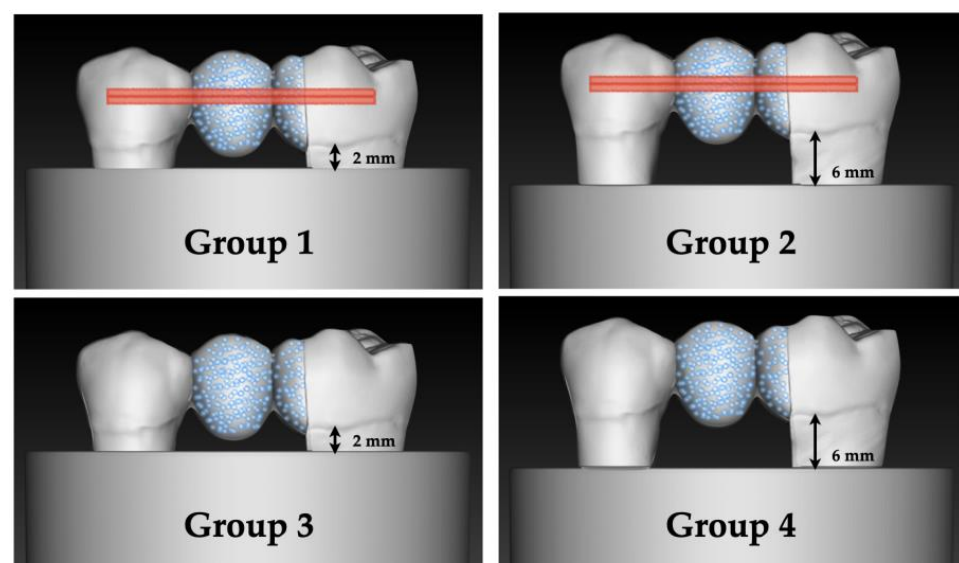


Figure 3. Schematic pictures of the 4 study groups.

2.5. Mechanical Testing

The samples were subjected to an accelerated fatigue-testing protocol [18], performed with a hydrodynamic testing machine (Instron ElektroPlus E3000, Norwood, MA, USA). Cyclic isometric loading was applied at the connector part of the restored units with a 5 mm wide, round-ended metallic tip (Figure 4). During the preloading, the samples had to endure a cyclic load at a frequency of 5 Hz. First, the load was continuously increased to 100 N in 5 s, then dynamic loading was applied with a force of 100 N for 5000 cycles. The load was then increased by 100 N each time up to 800 N, and 5000 cycles were completed for each 100 N increase. The teeth were loaded until fracture or until the total number of cycles was reached (40,000 cycles).



Figure 4. During the accelerated fatigue test, the load was applied at the connector part of the restored units with a 5 mm wide, round-ended metallic tip.

After the loading test, the fractures of all fractured specimens were observed visually and were classified into two categories according to the extent of the fracture line. A fracture was considered favorable (reparable) if the composite restoration fractured with or without the tooth structure coronally to the simulated bone level, but not below it. Fractures reaching below this level were considered unfavorable (irreparable).

3. Results

The Kaplan–Meier survival curves of the tested groups are presented in Figure 5, and the results of the post hoc log-rank pairwise comparisons (*Mantel–Cox*) are given in Table 3.

The fatigue resistance of Group 2 was significantly superior to Group 3 ($p = 0.004$) and Group 4 ($p = 0.018$), but the rest of the comparisons did not indicate a significant difference. Consequently, the first null hypothesis was rejected.

In terms of the fracture patterns (Table 4), most of the samples in Groups 1 and 2 survived, while Groups 3 and 4 were characterized by an almost equal number of favorable and unfavorable fractures. Therefore, the second null hypothesis regarding fracture patterns was rejected too.

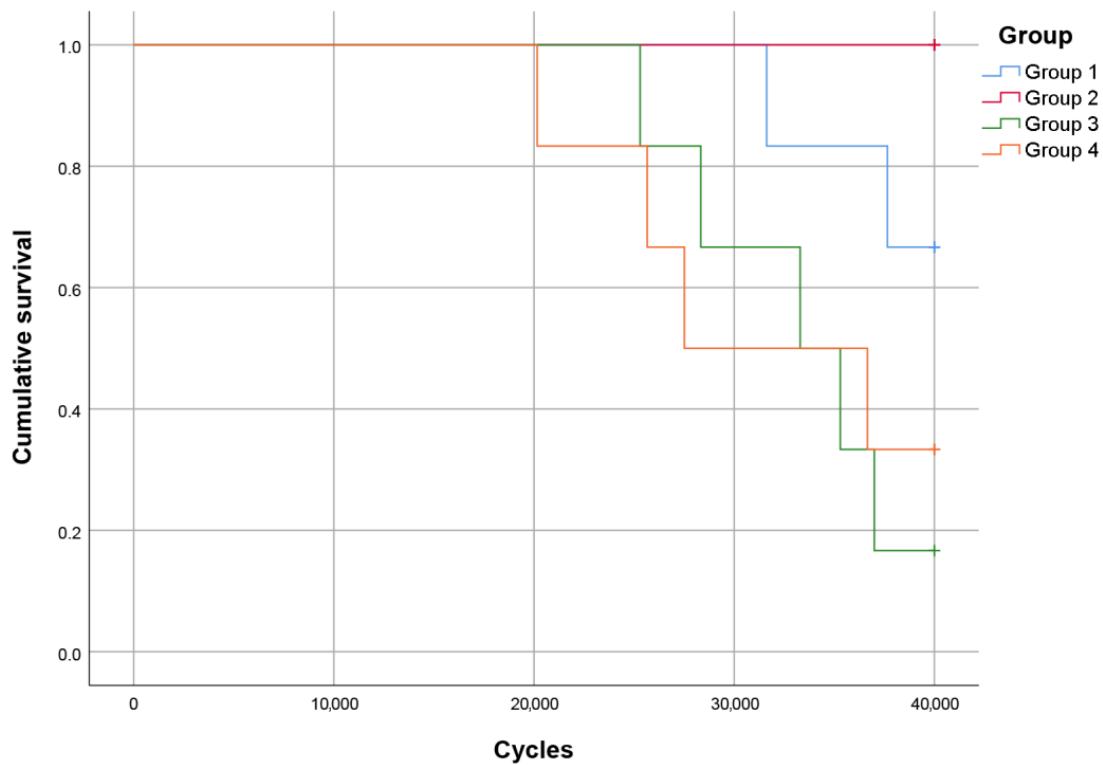


Figure 5. Kaplan–Meier survival curves.

Table 3. Results of the pairwise comparisons (Mantel–Cox). Asterisk (*) marks significant difference.

		Pairwise Comparisons							
		Group 1		Group 2		Group 3		Group 4	
Log Rank (Mantel-Cox)	GROUP	Chi-Square	Sig.	Chi-Square	Sig.	Chi-Square	Sig.	Chi-Square	Sig.
	Group 1			2.195	0.138	3.607	0.058	1.950	0.163
	Group 2	2.195	0.138			8.170	0.004 *	5.568	0.018 *
	Group 3	3.607	0.058	8.170	0.004 *			0.041	0.839
	Group 4	1.950	0.163	5.568	0.018 *	0.041	0.839		

Table 4. Fracture patterns.

	Survived	Fractured	Favorable Fracture	Unfavorable Fracture
Group 1	4	2	1	1
Group 2	6	0	-	-
Group 3	1	5	2	3
Group 4	2	4	2	2

4. Discussion

The present study focused on the possible effects of FRC system choice and the remaining bone level on the fatigue resistance of lower dissected molar teeth that were restored with direct, inlay-retained FRC bridges. As in the recent studies carried out by the authors, cyclic loading was used instead of static load-to-fracture testing in this study [23,30,31]. When testing the tooth-restoration units, cycling loading is considered to be more suitable to model oral clinical conditions than static testing, as during cyclic loading repetitive forces are generated, which is closer to the conditions of chewing [31]. Additionally, as pointed out by Le Bell-Rönnlöf, fatigue more often leads to the fracture of a restored tooth than static forces [38]. Accelerated fatigue was introduced as a rational middle ground

between the load-to-fracture test and other, more sophisticated and time-consuming fatigue tests [39], and it has been used in several studies since its introduction [40–42].

In this study, utilizing a combination of continuous glass fiber bundles and discontinuous, short fibers in the direct composite bridge (Group 2) significantly increased the fatigue resistance of the restored premolar–molar units compared to the groups utilizing only SFRCs as the reinforcement within the bridge (Group 3, $p = 0.004$ and Group 4, $p = 0.018$). Therefore, our first null hypothesis was rejected. The reason behind our initial results could be the unique structure of the used continuous fibers, along with the SFRCs. The everStick C&B (GC Europe) used in this research contains unidirectional pre-impregnated E-glass fiber bundles embedded in a PMMA (polymethyl methacrylate)/bis-GMA (bisphenol glycidyl dimethacrylate) matrix. Long, continuous, unidirectional E-glass fibers have an anisotropic property, meaning that they provide the greatest reinforcement against forces perpendicular to the direction of the fibers, which corresponds to the typical axial load in the posterior region [43]. A good impregnation of fibers with the surrounding matrix is important as fiber reinforcement is only successful when the loading force can be transferred from the matrix to the fiber [44]. This is ensured by the bis-GMA/PMMA matrix in case of the utilized everStick C&B. So far, everStick C&B has shown superior results in reinforcing composite bridges in terms of fracture strength compared to non-reinforced direct bridges [44]. Our results are in good agreement with a previous study by Garoushi et al., who evaluated the effect of the FRC substructure on the static load-bearing capacity of particulate filler composites and concluded that supporting particulate filler composites by the FRC substructure increased the load-bearing capacity of the material [45]. This is also in line with the work of Cekic-Nagas et al., who found that the addition of long fibers to the framework significantly affected the load-bearing capacity of FRC restorations compared to the ones that were only using SFRCs for reinforcement [19]. However, they used everX Posterior, which is the paste or packable version of SFRC.

Clinical reports found that debonding of the veneering composite, fiber exposure, and fracture at the pontic or at the connector area are the primary failure types occurring in FRC fixed dental prostheses [46]. To overcome these failures, the framework design and amount of fibers should be increased to improve the rigidity of these bridges [47]. In this pilot study, the flowable version of SFRC (everX Flow) was used with and without continuous fibers to reinforce direct composite bridges. While the packable version of SFRCs contains millimeter-long fibers, the flowable one contains micrometer-long ones [48]. Simultaneously, the aspect ratio is still ideal in the case of the flowable version (between 30 and 94) [48], and the smaller size of the fibers allows a greater volume fraction to be used during the manufacturing of the material compared to the packable version. Due to these features, a flowable SFRC has a little higher fracture toughness compared to the packable version and has also produced slightly better results when restoring major dentinal defects compared to the packable one [23,26]. The anisotropic property of the long fibers and the extreme number of fibers incorporated in the SFRC together might account for the better performance of the combination of short and long fibers compared to short fibers alone. This is in accordance with the findings of Keulemans et al., who evaluated the influence of the framework design on the load-bearing capacity of laboratory-made three-unit inlay-retained FRC bridges [49]. The highest load-bearing capacity was observed with FRC frameworks made of a combination of long, unidirectional FRC and SFRC.

Surprisingly, our results seem to suggest that the amount of periodontal support does not play a crucial role in the fatigue resistance when looking at each tested restorative technique, as the groups within a certain restorative technique with different levels of simulated periodontal support did not differ significantly (comparing Group 1 to 2, and Group 3 to 4). This is in agreement with our earlier findings, where we examined the mechanical behavior of root-amputated intracoronally splinted, periodontally compromised maxillary molars and the presence or absence of furcation involvement did not seem to influence the fatigue survival of the tested specimen [34]. At the same time, these findings contradict those of Soares et al., who found that the amount of bony support influenced the strain that

developed in the splinted teeth [50]. It must be noted, however, that Soares et al. examined lower front teeth. Furthermore, Szabó et al. found that furcation involvement as periodontal impairment was a significant factor in weakening root-amputated maxillary molars that were restored by either a direct filling or an overlay [4]. Note that in this study, splinted lower tooth pairs were tested, whereas Szabó et al. tested single upper molars, which might be the reason for the seemingly opposing results. The reason behind our findings might be due to the fact that the inlay-retained FRC bridge not only restores the edentulous space but simultaneously splints the involved teeth together. Splinting either with FRC or non-FRC restorations has long been the therapy of periodontally compromised teeth. However, our results regarding the influence of periodontal levels must be interpreted with caution as this is so far a pilot study and the amount of samples per group should be increased to strengthen the current findings.

In terms of fracture patterns, irreparable fractures occurred more frequently in the SFRC groups (Groups 3 and 4); thus, our second null hypothesis was also rejected. It should be emphasized that most of the samples in Groups 1 and 2 survived the accelerated fatigue testing cycles. This again shows the importance of combining continuous and discontinuous fibers in the restorative process of direct, inlay-retained bridges. Our results suggest that the amount of periodontal support does not seem to influence the fracture patterns of these bridge units as none of the units in Group 2 (continuous fibers and periodontally compromised situation) fractured during the mechanical testing. This is contrary to our previous findings [34], when upper maxillary, root-amputated teeth were examined, which could account for the different outcomes.

A visual analysis revealed that the ways of crack propagation were mostly oblique occlusally gingiva through the connector. SEM images of tested specimens showed that the crack path propagated from the loading surface (occlusally at connector area) to the inner part of composite restoration, where it was stopped/redirectioned by fibers (Figure 6). It is interesting to note that SFRCs were closely connected to the fiber bundle, which reduced the negative effects of having a weak link between them. Because of the semi-IPN (interpenetrating polymer network) polymer matrix structure, continuous glass fiber bundles (everStick C&B) have a good bonding ability with direct resin composite enabling reliable retained applications. This kind of interlocking or adhesion explains the performance of using both FRC systems together.

On the other hand, Tsujimoto and his colleagues determined that the relationship between mechanical properties and dentine bond durability of SFRCs using universal adhesives showed improvements compared to conventional PFC composites [51]. The ratios of shear fatigue strength and shear bond strength of SFRCs were higher than those of conventional PFC resins. In fact, the superior mechanical properties of SFRCs, especially fracture toughness, could improve the bond durability with adhesives.

We would like to emphasize that in all our tested groups, the external surfaces of the bridges were also made with flowable SFRCs. This was performed in order to maximize the amount of fibers in our restorations. Using flowable SFRCs without PFC coverage is in line with other studies [32,33,52]. According to the findings of Lassila et al., restorations made purely from flowable SFRCs show a significantly higher fracture resistance compared to covered SFRC restorations [51]. As pointed out by Garoushi and colleagues, if the SFRC-core is considered as a crack-stopper, the distance from the surface of the stress initiation point to the SFRC-core is of importance [32].

Finally, the design of this *in vitro* study has some strengths and limitations. The authors believe that the use of human teeth with similar dimensions, the effort put into standardization of the restored units, and the fact that cyclic loading was applied are obvious strengths. The novelty of the study lies within two features of the study design. Firstly, a flowable SFRC was used without PFC coverage together with unidirectional fibers to potentially strengthen the bridge. Secondly, different periodontal supporting levels have been simulated in this study. Not only that the literature lacks simulations of periodontally compromised situations in mechanical testing, but also, so far there has been no study

simulating these severe yet common conditions in the case of inlay-retained direct FRC composite bridges.



Figure 6. SEM images with different magnifications show how a crack is propagating inside the SFRC material (arrows) to stop when reaching the long fiber bundles in Groups 1 and 2.

The most important limitation is that a relatively low number of specimens were tested as this was a pilot investigation. Furthermore, a bridge with PFC coverage on its external surface should also be tested to see how much of the resistance is attributed to the presence or absence of SFRCs. This is a known limitation of all current in vitro mechanical testing studies, which should be addressed in the future.

5. Conclusions

Within the limitations of the study, it can be concluded that in the case of impaired periodontal support, the combination of continuous and discontinuous short glass fibers might increase the fatigue resistance of direct inlay-retained bridges compared to only SFRC-containing bridges. However, when the periodontal support is sound, there seems to be no benefit of adding continuous fibers to the SFRCs in direct composite bridges.

Author Contributions: Conceptualization, V.T.S., B.S. and M.F.; methodology, B.S., V.T.S., S.G. and M.F.; software, G.B.; validation, G.B.; formal analysis, L.L. and S.G.; investigation, V.T.S., C.M. and N.B.-T.; resources, M.F. and B.P.S.; data curation, M.F. and B.P.S.; writing—original draft preparation, V.T.S., B.S. and M.F.; writing—review and editing, M.F., L.L. and S.G.; visualization, B.S.; supervision, M.F.; project administration, M.F. and V.T.S.; funding acquisition, M.F. All authors have read and agreed to the published version of the manuscript.

Funding: This study was supported by the Bolyai János Research Scholarship (BO/701/20/5) and by the ÚNKP-22-5-SZTE New National Excellence Program of The Ministry for Innovation and Technology from the Source of National Research, Development and Innovation Fund, Hungary, and by the EU through the Economic Development and Innovation Operational Programme (GINOP-2.3.3-15-2016-00040).

Institutional Review Board Statement: The study was conducted according to the guidelines of the Declaration of Helsinki, and was approved by the Ethics Committee of the University of Szeged (4029).

Informed Consent Statement: Not applicable.

Data Availability Statement: Data are contained within the article.

Acknowledgments: We would like to thank Eija Sailynoja, Roosa Prinssi, and also the University of Szeged Centre of Excellence for Interdisciplinary Research, Development and Innovation, 3D Centre for all their valuable help in this collaboration.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Krebs, M.; Kesar, N.; Begić, A.; Von Krockow, N.; Nentwig, G.; Weigl, P. Incidence and prevalence of peri-implantitis and peri-implant mucositis 17 to 23 (18.9) years postimplant placement. *Clin. Implant. Dent. Relat. Res.* **2019**, *21*, 1116–1123. [[CrossRef](#)] [[PubMed](#)]
2. Wada, M.; Mameno, T.; Otsuki, M.; Kani, M.; Tsujioka, Y.; Ikebe, K. Prevalence and risk indicators for peri-implant diseases: A literature review. *Jpn. Dent. Sci. Rev.* **2021**, *57*, 78–84. [[CrossRef](#)] [[PubMed](#)]
3. Sousa, V.; Mardas, N.; Farias, B.; Petrie, A.; Needleman, I.; Spratt, D.; Donos, N. A systematic review of implant outcomes in treated periodontitis patients. *Clin. Oral Implant. Res.* **2015**, *27*, 787–844. [[CrossRef](#)]
4. Szabó, B.; Garoushi, S.; Braunitzer, G.; Baráth, Z.; Fráter, M. Fracture behavior of root-amputated teeth at different amount of periodontal support—a preliminary in vitro study. *BMC Oral Health* **2019**, *19*, 261. [[CrossRef](#)]
5. Megarbane, J.-M.; Kassir, A.R.; Mokbel, N.; Naaman, N. Root Resection and Hemisection Revisited. Part II: A Retrospective Analysis of 195 Treated Patients with Up to 40 Years of Follow-up. *Int. J. Periodontics Restor. Dent.* **2018**, *38*, 783–789. [[CrossRef](#)] [[PubMed](#)]
6. El Sayed, N.; Cosgarea, R.; Rahim, S.; Giess, N.; Krisam, J.; Kim, T.-S. Patient-, tooth-, and dentist-related factors influencing long-term tooth retention after resective therapy in an academic setting—a retrospective study. *Clin. Oral Investig.* **2019**, *24*, 2341–2349. [[CrossRef](#)]
7. Desanctis, M.; Murphy, K.G. The role of resective periodontal surgery in the treatment of furcation defects. *Periodontology 2000* **2000**, *22*, 154–168. [[CrossRef](#)]
8. Carnevale, G.; Pontoriero, R.; Hürzeler, M.B. Management of furcation involvement. *Periodontology 2000* **1995**, *9*, 69–89. [[CrossRef](#)] [[PubMed](#)]
9. Naveen, Y.G.; Patel, J.R.; Parikh, P.; Shah, K. Alternatives for restoration of a hemisected mandibular molar. *BMJ Case Rep.* **2014**, *2014*, bcr2013010275. [[CrossRef](#)]
10. Dannewitz, B.; Krieger, J.K.; Hüsing, J.; Eickholz, P. Loss of molars in periodontally treated patients: A retrospective analysis five years or more after active periodontal treatment. *J. Clin. Periodontol.* **2006**, *33*, 53–61. [[CrossRef](#)]
11. Ahmed, K.E.; Li, K.Y.; Murray, C.A. Longevity of fiber-reinforced composite fixed partial dentures (FRC FPD)—Systematic review. *J. Dent.* **2017**, *61*, 1–11. [[CrossRef](#)] [[PubMed](#)]
12. Perea-Lowery, L.; Vallittu, P.K. Framework design and pontics of fiber-reinforced composite fixed dental prostheses—An overview. *J. Prosthodont. Res.* **2018**, *62*, 281–286. [[CrossRef](#)] [[PubMed](#)]
13. Vallittu, P.K.; Shinya, A.; Baraba, A.; Kerr, I.; Keulemans, F.; Kreulen, C.; Lassila, L.; Malmstrom, H.; Novotny, R.; Peumans, M.; et al. Fiber-reinforced composites in fixed prosthodontics—Quo vadis? *Dent. Mater.* **2017**, *33*, 877–879. [[CrossRef](#)] [[PubMed](#)]
14. Perrin, P.; Meyer-Lueckel, H.; Wierichs, R. Longevity of immediate rehabilitation with direct fiber reinforced composite fixed partial dentures after up to 9 years. *J. Dent.* **2020**, *100*, 103438. [[CrossRef](#)]
15. Vallittu, P.; Matinlinna, J. Types of Frcs Used in Dentistry. In *Clinical Guide to Principles of Fiber-Reinforced Composites in Dentistry*; Vallittu, P., Özcan, M., Eds.; Woodhead Publishing Ltd: Cambridge, MA, USA, 2017; pp. 11–34.

16. Vallittu, P.K. Survival rates of resin-bonded, glass fiber-reinforced composite fixed partial dentures with a mean follow-up of 42 months: A pilot study. *J. Prosthet. Dent.* **2004**, *91*, 241–246. [[CrossRef](#)] [[PubMed](#)]
17. van Heumen, C.C.M.; Kreulen, C.M.; Creugers, N.H.J. Clinical studies of fiber-reinforced resin-bonded fixed partial dentures: A systematic review. *Eur. J. Oral Sci.* **2009**, *117*, 1–6. [[CrossRef](#)] [[PubMed](#)]
18. Kumbuloglu, O.; Özcan, M.; User, A. Fracture Strength of Direct Surface-retained Fixed Partial Dentures: Effect of Fiber Reinforcement versus the Use of Particulate Filler Composites Only. *Dent. Mater. J.* **2008**, *27*, 195–202. [[CrossRef](#)] [[PubMed](#)]
19. Cekic-Nagas, I.; Egilmez, F.; Ergun, G.; Vallittu, P.K.; Lassila, L.V.J. Load-bearing capacity of novel resin-based fixed dental prosthesis materials. *Dent. Mater. J.* **2018**, *37*, 49–58. [[CrossRef](#)]
20. Ang, Y.; Tan, C.G.; Yahaya, N. In-vitro performance of posterior fiber reinforced composite (FRC) bridge with different framework designs. *Dent. Mater. J.* **2021**, *40*, 584–591. [[CrossRef](#)]
21. Ellakwa, A.E.; Shortall, A.C.; Shehata, M.K.; Marquis, P.M. The influence of fibre placement and position on the efficiency of reinforcement of fibre reinforced composite bridgework. *J. Oral Rehabil.* **2001**, *28*, 785–791. [[CrossRef](#)]
22. Özcan, M.; Breuklander, M.; Salihoglu-Yener, E. Fracture resistance of direct inlay-retained adhesive bridges: Effect of pontic material and occlusal morphology. *Dent. Mater. J.* **2012**, *31*, 514–522. [[CrossRef](#)] [[PubMed](#)]
23. Molnár, J.; Fráter, M.; Sály, T.; Braunitzer, G.; Vallittu, P.K.; Lassila, L.; Garoushi, S. Fatigue performance of endodontically treated molars restored with different dentin replacement materials. *Dent. Mater.* **2022**, *38*, e83–e93. [[CrossRef](#)]
24. Fráter, M.; Sály, T.; Vincze-Bandi, E.; Volom, A.; Braunitzer, G.; Balázs Szabó, P.; Garoushi, S.; Forster, A. Fracture Behavior of Short Fiber-Reinforced Direct Restorations in Large MOD Cavities. *Polymers* **2021**, *13*, 2040. [[CrossRef](#)] [[PubMed](#)]
25. Fráter, M.; Sály, T.; Braunitzer, G.; Szabó, P.B.; Lassila, L.; Vallittu, P.K.; Garoushi, S. Fatigue failure of anterior teeth without ferrule restored with individualized fiber-reinforced post-core foundations. *J. Mech. Behav. Biomed. Mater.* **2021**, *118*, 104440. [[CrossRef](#)]
26. Fráter, M.; Sály, T.; Néma, V.; Braunitzer, G.; Vallittu, P.; Lassila, L.; Garoushi, S. Fatigue failure load of immature anterior teeth: Influence of different fiber post-core systems. *Odontology* **2020**, *109*, 222–230. [[CrossRef](#)] [[PubMed](#)]
27. Garoushi, S.; Vallittu, P.K. Mechanical Properties and Wear of Five Commercial Fibre-Reinforced Filling Materials. *Chin. J. Dent. Res.* **2017**, *20*, 137–143. [[CrossRef](#)] [[PubMed](#)]
28. Garoushi, S.; Gargoum, A.; Vallittu, P.K.; Lassila, L. Short fiber-reinforced composite restorations: A review of the current literature. *J. Investig. Clin. Dent.* **2018**, *9*, e12330. [[CrossRef](#)]
29. Garoushi, S.; Lassila, L. Fibre-reinforced Composite in Clinical Dentistry. *Chin. J. Dent. Res.* **2009**, *12*, 7–14.
30. Fráter, M.; Sály, T.; Jókai, B.; Braunitzer, G.; Säilynoja, E.; Vallittu, P.K.; Lassila, L.; Garoushi, S. Fatigue behavior of endodontically treated premolars restored with different fiber-reinforced designs. *Dent. Mater.* **2021**, *37*, 391–402. [[CrossRef](#)]
31. Fráter, M.; Sály, T.; Molnár, J.; Braunitzer, G.; Lassila, L.; Vallittu, P.K.; Garoushi, S. Fatigue performance of endodontically treated premolars restored with direct and indirect cuspal coverage restorations utilizing fiber-reinforced cores. *Clin. Oral Investig.* **2021**, *26*, 3501–3513. [[CrossRef](#)]
32. Garoushi, S.; Sungur, S.; Boz, Y.; Ozkan, P.; Vallittu, P.K.; Uctasli, S.; Lassila, L. Influence of short-fiber composite base on fracture behavior of direct and indirect restorations. *Clin. Oral Investig.* **2021**, *25*, 4543–4552. [[CrossRef](#)]
33. Mangoush, E. Influence of Short Fiber Reinforced Composites on Fracture Resistance of Single-Structure Restorations. *Eur. J. Prosthodont. Restor. Dent.* **2020**, *28*, 189–198. [[CrossRef](#)] [[PubMed](#)]
34. Szabó, V.T.; Szabó, B.; Paczona, B.; Mészáros, C.; Braunitzer, G.; Szabó, P.B.; Garoushi, S.; Fráter, M. The biomechanical effect of root amputation and degree of furcation involvement on intracoronally splinted upper molar teeth – An in vitro study. *J. Mech. Behav. Biomed. Mater.* **2022**, *129*, 105143. [[CrossRef](#)] [[PubMed](#)]
35. Cara, R.; Fleming, G.; Palin, W.; Walmsley, A.; Burke, F. Cuspal deflection and microleakage in premolar teeth restored with resin-based composites with and without an intermediary flowable layer. *J. Dent.* **2007**, *35*, 482–489. [[CrossRef](#)] [[PubMed](#)]
36. Szabó, V.T.; Szabó, B.; Tarjányi, T.; Szőke-Trenyik, E.; Fráter, M. Analog and digital modeling of sound and impaired periodontal supporting tissues during mechanical testing. *Analecta Tech. Szeged.* **2021**, *15*, 84–97. [[CrossRef](#)]
37. Szabó, B.; Gabriella, E.; Fráter, M. Gyökéramputált és betéttel restaurált felső moláris fogak törési ellenállásának in vitro vizsgálata. *Fogorvosi Szle.* **2017**, *110*, 111–116. [[CrossRef](#)]
38. Le Bell-Rönnlöf, A.-M.; Lassila, L.V.; Kangasniemi, I.; Vallittu, P.K. Load-bearing capacity of human incisor restored with various fiber-reinforced composite posts. *Dent. Mater.* **2011**, *27*, e107–e115. [[CrossRef](#)]
39. Magne, P.; Carvalho, A.; Bruzi, G.; Anderson, R.; Maia, H.; Giannini, M. Influence of No-Ferrule and No-Post Buildup Design on the Fatigue Resistance of Endodontically Treated Molars Restored with Resin Nanoceramic CAD/CAM Crowns. *Oper. Dent.* **2014**, *39*, 595–602. [[CrossRef](#)]
40. Soares, L.M.; Razaghy, M.; Magne, P. Optimization of large MOD restorations: Composite resin inlays vs. short fiber-reinforced direct restorations. *Dent. Mater.* **2018**, *34*, 587–597. [[CrossRef](#)]
41. Lazari, P.C.; de Carvalho, M.A.; Del Bel Cury, A.A.; Magne, P. Survival of extensively damaged endodontically treated incisors restored with different types of posts-and-core foundation restoration material. *J. Prosthet. Dent.* **2018**, *119*, 769–776. [[CrossRef](#)]
42. Gresnigt, M.M.; Özcan, M.; Carvalho, M.; Lazari, P.; Cune, M.S.; Razavi, P.; Magne, P. Effect of luting agent on the load to failure and accelerated-fatigue resistance of lithium disilicate laminate veneers. *Dent. Mater.* **2017**, *33*, 1392–1401. [[CrossRef](#)] [[PubMed](#)]
43. Vallittu, P.K. High-aspect ratio fillers: Fiber-reinforced composites and their anisotropic properties. *Dent. Mater.* **2015**, *31*, 1–7. [[CrossRef](#)] [[PubMed](#)]

44. Özcan, M.; Koekoek, W.; Pekkan, G. Load-bearing capacity of indirect inlay-retained fixed dental prostheses made of particulate filler composite alone or reinforced with E-glass fibers impregnated with various monomers. *J. Mech. Behav. Biomed. Mater.* **2012**, *12*, 160–167. [[CrossRef](#)]
45. Garoushi, S.; Lassila, L.V.; Tezvergil, A.; Vallittu, P.K. Load bearing capacity of fibre-reinforced and particulate filler composite resin combination. *J. Dent.* **2006**, *34*, 179–184. [[CrossRef](#)] [[PubMed](#)]
46. Perea, L.; Matinlinna, J.P.; Tolvanen, M.; Vallittu, P.K. Fracture behavior of pontics of fiber-reinforced composite fixed dental prostheses. *Dent. Mater. J.* **2015**, *34*, 746–753. [[CrossRef](#)]
47. Freilich, M.A.; Meiers, J.C.; Duncan, J.P.; Eckrote, K.A.; Goldberg, A.J. Clinical evaluation of fiber-reinforced fixed bridges. *J. Am. Dent. Assoc.* **2002**, *133*, 1524–1534. [[CrossRef](#)]
48. Lassila, L.; Keulemans, F.; Säilynoja, E.; Vallittu, P.K.; Garoushi, S. Mechanical properties and fracture behavior of flowable fiber reinforced composite restorations. *Dent. Mater.* **2018**, *34*, 598–606. [[CrossRef](#)]
49. Keulemans, F.; Lassila, L.V.; Garoushi, S.; Vallittu, P.K.; Kleverlaan, C.J.; Feilzer, A.J. The influence of framework design on the load-bearing capacity of laboratory-made inlay-retained fibre-reinforced composite fixed dental prostheses. *J. Biomech.* **2009**, *42*, 844–849. [[CrossRef](#)]
50. Soares, P.B.F.; Neto, A.J.F.; Magalhães, D.; Versluis, A.; Soares, C.J. Effect of bone loss simulation and periodontal splinting on bone strain: Periodontal splints and bone strain. *Arch. Oral Biol.* **2011**, *56*, 1373–1381. [[CrossRef](#)]
51. Tsujimoto, A.; Barkmeier, W.W.; Takamizawa, T.; Watanabe, H.; Johnson, W.W.; Latta, M.A.; Miyazaki, M. Relationship between mechanical properties and bond durability of short fiber-reinforced resin composite with universal adhesive. *Eur. J. Oral Sci.* **2016**, *124*, 480–489. [[CrossRef](#)]
52. Lassila, L.; Säilynoja, E.; Prinssi, R.; Vallittu, P.K.; Garoushi, S. Bilayered composite restoration: The effect of layer thickness on fracture behavior. *Biomater. Investig. Dent.* **2020**, *7*, 80–85. [[CrossRef](#)] [[PubMed](#)]

Disclaimer/Publisher’s Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.