

ARCHAOMETRICAL STUDIES ON SOME BRONZE BUCKLES WITH PORTABLE (HANDHELD) XRF SPECTROSCOPY

ZOLTÁN MAY*–GERGELY SZENTHE**

*Hungarian Academy of Sciences, Research Center for Natural Sciences,
Institute of Material and Environmental Chemistry, H–1117 Budapest, Hungary
may.zoltan@ttk.mta.hu

**Hungarian National Museum, Department of Archaeology,
H–1088 Budapest, Hungary, Múzeum krt. 14–16.
szenthe.gergely@hnm.hu

Abstract: Portable handheld X-Ray Fluorescence Spectroscopy (pXRF) is very effective and widely used technique for chemical analysis in field of archaeometry. The most advantageous feature of this technique is the possibility of analysing objects, artefacts on the spot without any sample-taking. In this study raw materials of 31 buckles from 7th century AD made of various kinds of bronze and silver alloys were analyzed to check similarities or differences between these objects via chemical analysis. Concentration ratios and distributions of alloying (Cu, Sn, Pb, Ag) and minor elements (Sb, Bi, Zn, Au) in material of bronze artifacts may have useful information suggesting important data about provenance and technology. Our recent study 27 bronze and 4 silver buckles were analyzed by pXRF and the results were used in statistical evaluation in order to get closer to provenance of raw materials and alloying technologies.

INTRODUCTION

The object-type the single specimens of which are analyzed in the recent paper is a simple but characteristic phenomenon of the ‘Early’ and ‘Middle Avar Period’ of the 6th and 7th century. Although the most contemporary buckles and belt fittings in the Carpathian Basin belong to or are derived from a Byzantine, or more generally, European Mediterranean material culture, the buckle type of flat, shield-shaped mount is most probable of Eastern-European origin.

Technological data expand the results of the morphological analysis. There are but just a few and old measurements for alloy compositions, which are mostly not comparable with the more recent analyses, and which base mainly on younger material (*en masse* cast artifacts /belt fittings/ of the Late Avar Period, 8th century).¹ In lack of comparative material the recent project raises more questions than it answers.

Only an extensive program of material composition analyses can bring answers for the questions, whether there are any differences between the material composition of Byzantine cast objects and the object-types of the northern peripheries; and if so, whether there is a cultural or economical significance of the differences; or whether there are chronological changes in the alloy compositions.² As most crucial from the point of view of a technological historical perspective, we can put the question whether tendencies indicating the planned, systematical exploitation and traffic of certain resources will be reconstructable in the future.

¹ KÖLTŐ 1982; DAIM 1987; DAIM 2000.

² For the latter see DAIM 2000.

MATERIAL AND METHODS

The sampling referred to the geographical and chronological groups of the objects revealed by the archaeological evaluation.³ The selection is representative for the earlier group of objects (characteristic mainly for Transdanubia) and for the younger group as well (with an accent of the regional distribution East of the Danube, and mostly in well-furnished weapon graves).

This group of buckles was chemically analyzed by X-ray fluorescence method for obtain detailed information about raw material of these specimens. The group consists of 27 bronze (several type) and 4 silver buckles which were produced and used in the 7th century AD and were found (excavated) from several area in Hungary. The portable XRF analyzer used for this study was a Thermo Scientific Niton X13t 900 GOLDD+ (Geometrically Optimized Large Area Drift Detector) with 50 kV X-ray tube with silver target (Ag anode). This apparatus has some company-preset calibrations for given matrices and in our case “General Metals” and “Precious Metals” were used (both were applied for silver objects and first one for all the others). For all analysis two energy filters for irradiation were applied including Main, and High filter. The third one (Light filter) was not used in order to get complete and real composition of the studied alloys eliminating non-relevant elements (Si, Al, Ti) coming from surface contaminations (soil or dust layer). Measuring time was 60 sec. in all cases using 30-30 sec. for each filter. Measuring spot size (irradiation area on the object surface) was 8 mm in diameter. Before measuring a little area was cleaned and rasped on the surface of every object to remove corrosion products and contaminations (dust, soil, etc.) to measure real material of the buckles. Following elements can be measured by pXRF: Sb, Sn, Cd, Pd, Ag, Ru, Mo, Nb, Zr, Bi, Pb, Se, Au, W, Zn, Cu, Ni, Co, Fe, Mn, Cr, V, In, Rh, Pt, Ir, Ga. Among these we used only relevant elements for evaluation data. Standardless fundamental parameters method with Compton-normalization is used by the XRF apparatus for quantitative analysis and results were also checked by viewing the corresponding spectra with NDT software (Niton Data Transfer, version 8.0.0). Mathematical and statistical data processing was done with Excel and Statistica 12 softwares.

RESULTS AND CONCLUSIONS

Chemical composition data of 27 bronze and 4 silver buckles obtained by pXRF analysis are in *Table 1*. As it can be seen in the tree diagram (dendogram) in figure 1 the 4 silver buckles form a very different group from the other buckles made of Cu alloys. The following examination done in present work basically refers to buckles made of bronze. The number of silver buckles studied here is very low (four objects) so there is no use making statistical calculations with these. The main information is the high level of similarity between the two silver buckles from Ozora with number 275.1871.28 and 275.1871.25a (see *Fig. 1*). There are two bronze objects which was considered to be the parts of the Kunágota grave find and to form a couple although the affiliation was dubious; now by this analysis this is probably proved.

If cluster analysis is performed on the 27 bronze objects without silver ones we get the tree diagram (dendogram) seeing below (*Fig. 2*) where four main groups can be distinguished with one outlier with significantly high zinc concentration (6.1937.11 from Kecel). From left to right the first group contains five objects with high concentration of lead and tin simultaneously (69.1858.13–2; 106.950.2; 48.1924.9; 12.1935.14; 22.1932.101). In the next group including 7 objects there are two couples with very similar chemical composition (104.1909.73 and 69.1858.13–1; 55.28.88 and 106.950.13a) despite of their different occurrences. In this group there is a buckle made of almost pure copper (> 98 %, red copper) which is not to be considered as bronze due to this chemical composition. In the third group there are four buckles with higher antimony concentrations (106.950.10a; 48.1924.26; 69.1.71; 69.1.170). In the fourth group (10 objects) there are also two couples of buckles according to their similar material (93.1900.43 and 69.1.42; 37.1887.17 and 69.1.95) but their origins are different either as in the previous case. Performing cluster analysis on the chemical elements can be also informative (see *Fig. 3*) where grouping of these constituents may carry useful information about raw materials and ores these objects was made of (provenance

³ See SZENTHE in the recent volume.

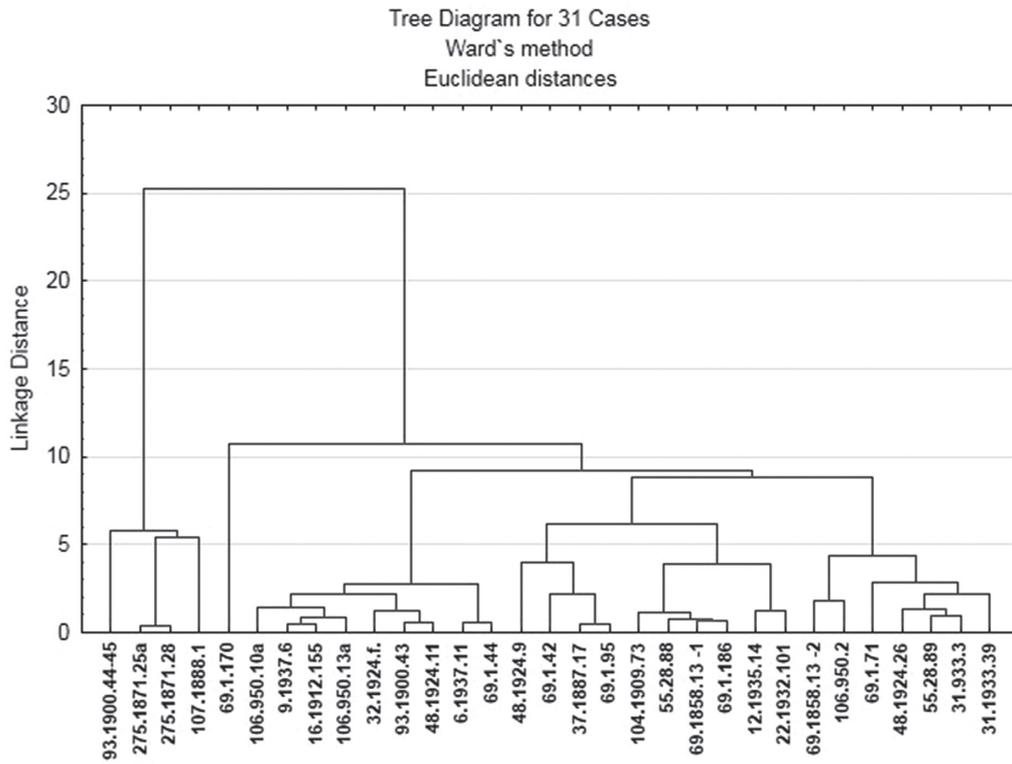


Fig. 1. Result of cluster analysis (dendrogram) performed on all the 31 buckles (bronze and silver)

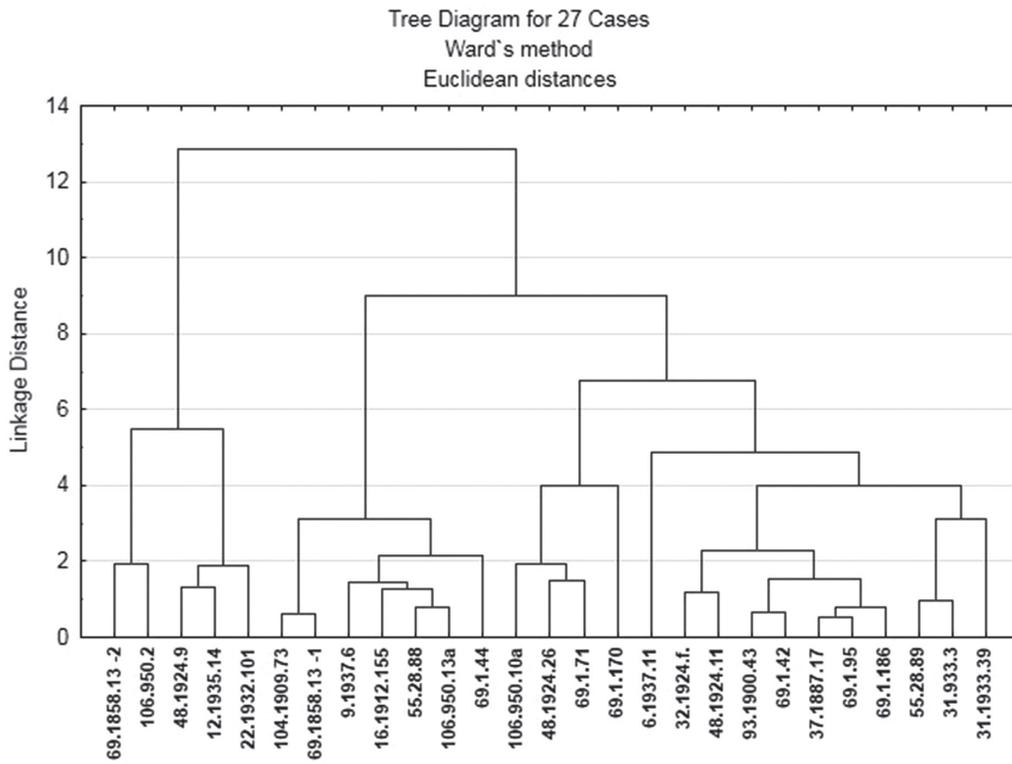


Fig. 2. Result of cluster analysis (dendrogram) performed only the 27 bronze buckles (without silver)

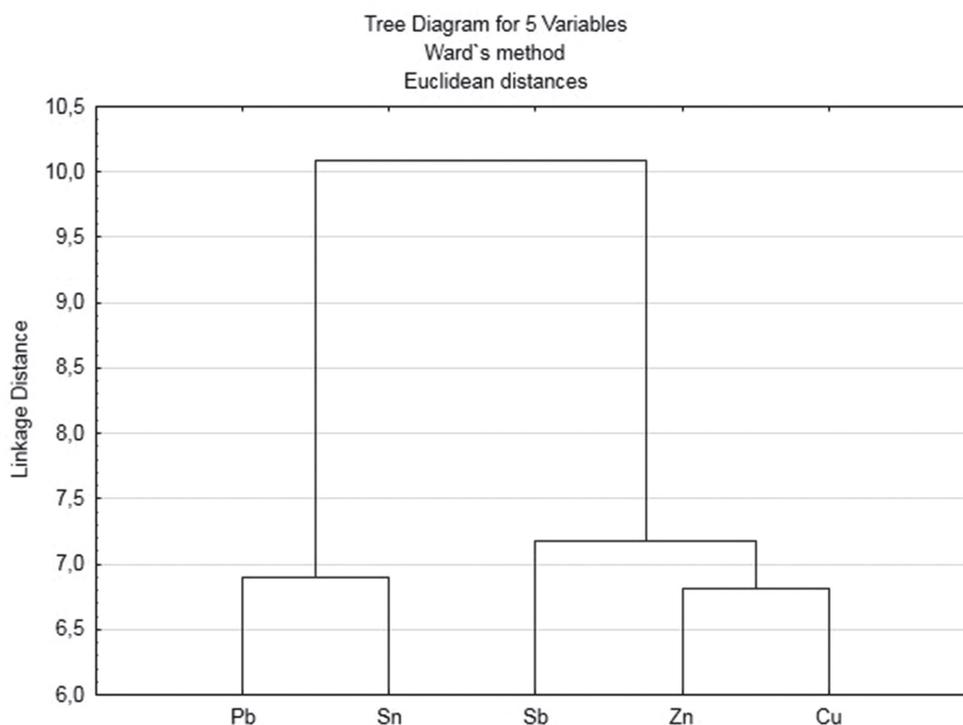


Fig. 3. Result of cluster analysis (dendrogram) using the alloying elements

studies). While some buckles with higher concentrations of one or some elements than the others form groups and couples in figures of factor and cluster analysis (*Fig. 4a, 4b*), the grouping according to their occurrences does not follow these tendencies and does not show these groups (see *Fig. 5a, 5b*). In principal component analysis (PCA) figures (*Fig. 6a, 6b*) the chemical elements measured by pXRF can be seen and the directions where a given element or elements dominate which can be compared with factor analysis figures. With this comparison we can clearly see which elements cause separation of the specimens into groups during statistical evaluations. The results in present study show the great heterogeneity of this collection and it is also can be seen that traffic and usage of raw materials and ores was not well organized and well planned. This conclusion is supported by statistical evaluations and figures mentioned above where composition of buckles belonging to given groups varies in wide range. Because of this we will continue this measurement on further objects which will be selected with other historical and archaeological considerations.

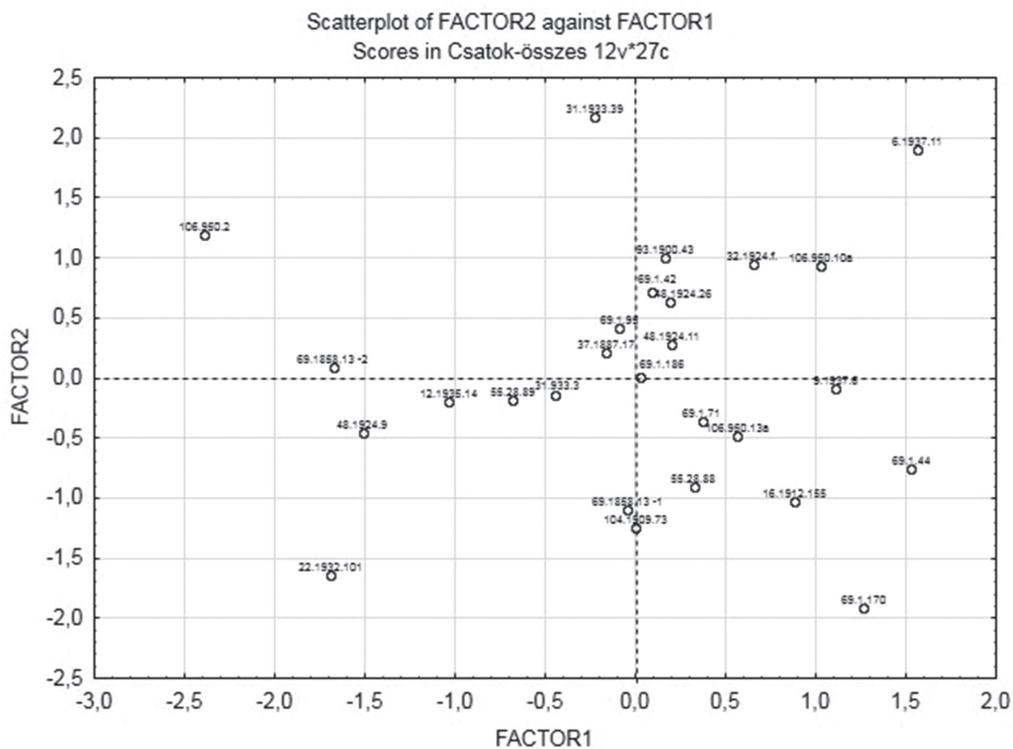


Fig. 4a. Factor analysis performed on the 27 bronze buckles

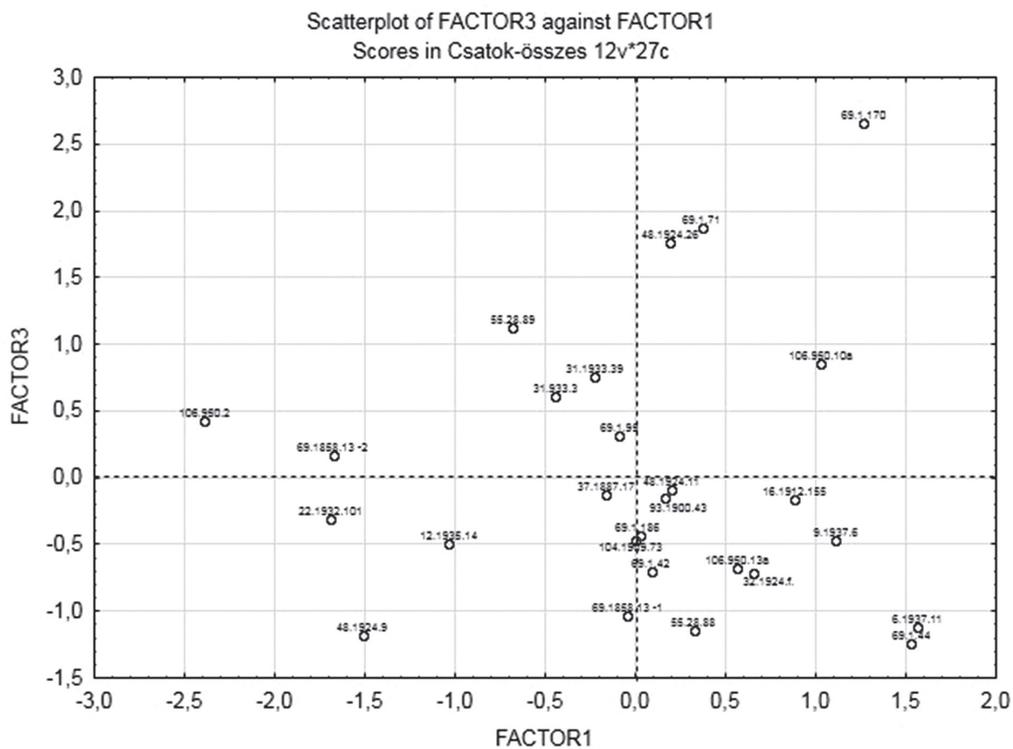


Fig. 4b. Factor analysis performed on the 27 bronze buckles

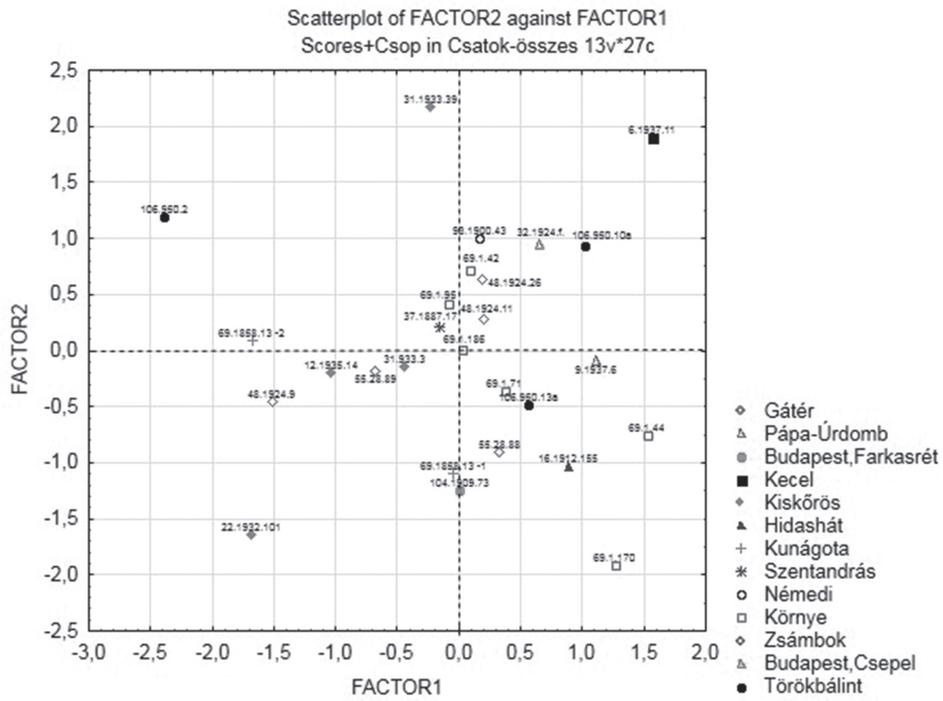


Fig. 5a. Factor analysis performed on the 27 bronze buckles with grouping according their occurrences

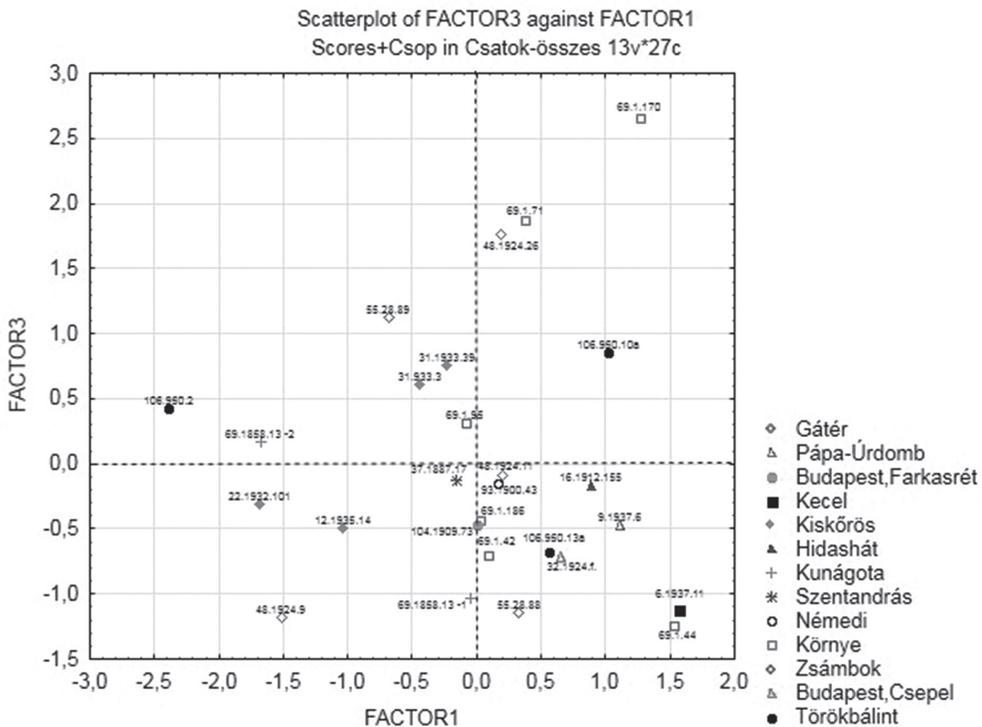


Fig. 5b. Factor analysis performed on the 27 bronze buckles with grouping according their occurrences

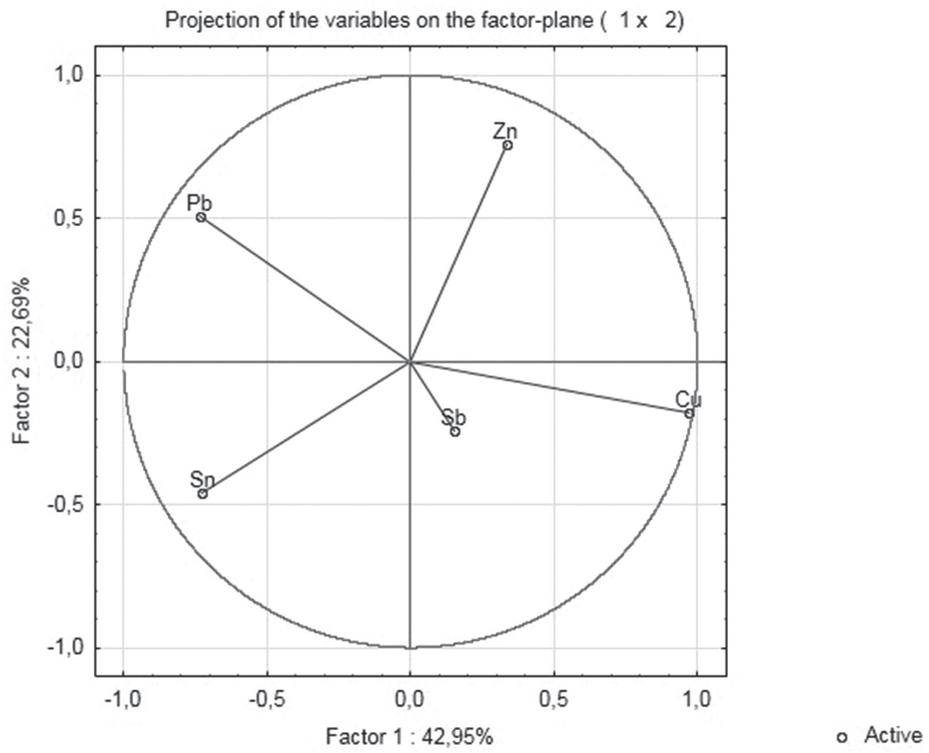


Fig. 6a. Principal component analysis performed on 27 bronze buckles

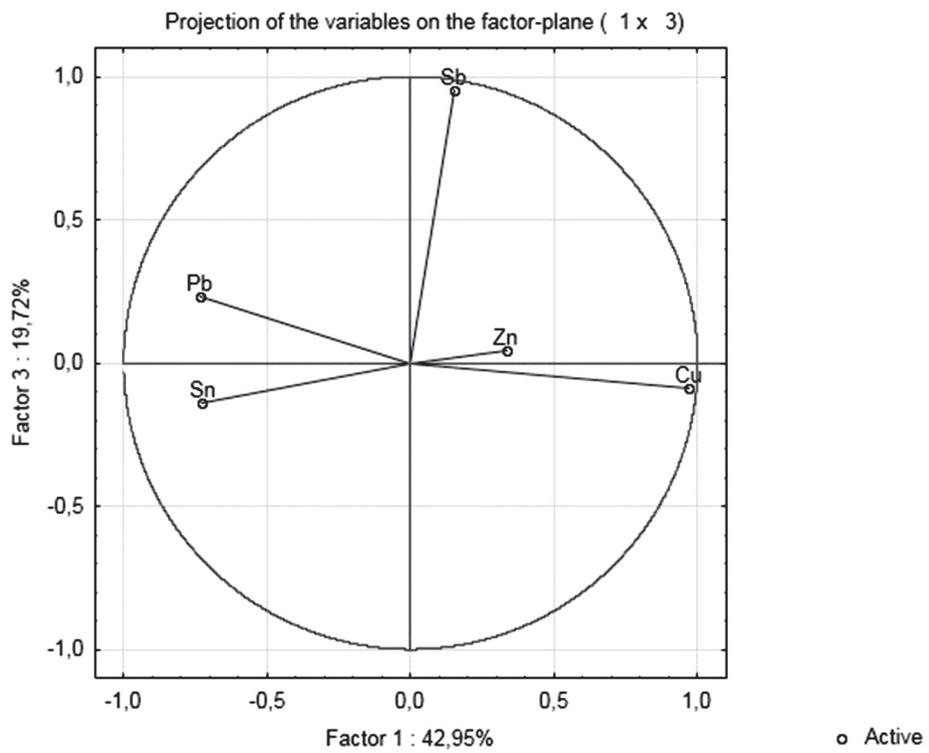


Fig. 6b. Principal component analysis performed on 27 bronze buckles

Table 1. Elemental composition of analyzed buckle specimens. Values are in % w/w. lod = limit of detection.
Lod values in % w/w: Zn: 0.04; Sb: 0.01; Bi: 0.02; Ag: 0.02; Au: 0.01

Cat. Number	Occurance	Cu	Sn	Pb	Zn	Sb	Bi	Ag	Au
31.1933.39	Kiskőrös	73.49	1.36	21.41	3.24	0.11	< lod	< lod	< lod
22.1932.101	Kiskőrös	64.79	26.61	7.70	0.16	0.11	< lod	< lod	< lod
31.933.3	Kiskőrös	76.16	7.66	15.09	0.27	0.13	< lod	< lod	< lod
12.1935.14	Kiskőrös	67.93	20.88	8.06	2.32	0.09	< lod	< lod	< lod
69.1.186	Környe	79.11	11.25	7.00	1.94	0.09	< lod	< lod	< lod
69.1.170	Környe	92.24	5.99	0.71	< lod	0.30	< lod	< lod	< lod
69.1.95	Környe	76.80	9.10	10.85	2.18	0.12	< lod	< lod	< lod
69.1.71	Környe	79.69	11.96	4.89	2.70	0.24	< lod	< lod	< lod
69.1.42	Környe	77.93	9.84	7.85	2.94	0.06	< lod	< lod	< lod
69.1.44	Környe	98.03	0.61	1.04	0.04	0.05	< lod	< lod	< lod
48.1924.9	Zsámbok	65.15	21.26	10.71	1.00	0.04	< lod	< lod	< lod
48.1924.11	Zsámbok	81.73	5.30	11.25	1.28	0.09	< lod	< lod	< lod
48.1924.26	Zsámbok	77.81	6.32	12.38	2.70	0.21	< lod	< lod	< lod
106.950.2	Törökbálint	57.02	10.36	32.01	0.12	0.08	< lod	< lod	< lod
106.950.13a	Törökbálint	86.54	7.51	4.72	0.88	0.08	< lod	< lod	< lod
106.950.10a	Törökbálint	85.39	3.82	6.52	3.72	0.16	< lod	< lod	< lod
107.1888.1	Ozora	10.82	0.60	0.61	0.32	< lod	0.10	81.92	5.51
275.1871.28	Ozora	12.06	0.96	3.18	0.05	< lod	0.07	82.30	1.27
275.1871.25a	Ozora	8.09	1.01	2.45	< lod	< lod	0.07	87.10	1.25
69.1858.13 -1	Kunágota	81.54	13.70	3.73	0.30	0.06	< lod	< lod	< lod
69.1858.13 -2	Kunágota	64.30	14.27	20.64	0.26	0.09	< lod	< lod	< lod
93.1900.43	Némedi	78.33	7.93	9.95	3.20	0.09	< lod	< lod	< lod
93.1900.44-45	Némedi	20.65	0.56	0.50	1.75	< lod	0.28	74.86	1.34
55.28.88	Gátér	85.74	9.14	4.45	< lod	0.05	< lod	< lod	< lod
55.28.89	Gátér	72.54	10.95	14.87	0.82	0.17	< lod	< lod	< lod
104.1909.73	Budapest, Farkasrét	81.45	14.23	3.30	0.39	0.10	< lod	< lod	< lod
32.1924.f.	Budapest, Csepel	84.91	2.54	9.57	2.35	0.05	< lod	< lod	< lod
16.1912.155	Hidashát	90.60	5.52	3.31	0.06	0.11	< lod	< lod	< lod
37.1887.17	Szentandrás	77.06	9.95	10.17	1.77	0.10	< lod	< lod	< lod
9.1937.6	Pápa-Úrdomb	90.36	4.41	2.87	1.80	0.09	< lod	< lod	< lod
6.1937.11	Kecel	89.74	2.30	2.22	5.40	0.04	< lod	< lod	< lod

REFERENCES

- DAIM 1987 = F. DAIM: Das awarische Gräberfeld von Leobersdorf, Niederösterreich. Studien zur Archäologie der Awaren 3. Wien 1987.
- DAIM 2000 = F. DAIM: „Byzantinische“ Gürtelgarnituren des 8. Jahrhunderts. In: F. Daim (Hrsg.): Die Awaren am Rand der byzantinischen Welt. Monographien zur Frühgeschichte und Mittelalterarchäologie 7. 2000, 77–204.
- KÖLTŐ 1982 = L. KÖLTŐ: Avar kori bronztárgyak röntgenemissziós analízise (X-ray emission analysis of bronze objects from the Avar Age). SMK 5/1 (1982) 5–68.